




# **VINTAGE ZR**

**ZR Bond Porcelain** 

# **Instructions for Use**

SHOFU INC.







#### Instruction for use

VINTAGE ZR porcelain system has been developed especially for the metal free restoration based on extra strong zirconium oxide frameworks according to the latest research in porcelain knowledge.

In combination with these substructures it offers unlimited possibilities in the reproduction of life like appearance for crowns and bridge works.

Opaque liners ensure the bonding to the zirconium frameworks, eliminate the whiteness issue and provide a patient specific coloration.

In addition VINTAGE ZR offers the light-optical aspects of natural teeth because of the micro fine particle structure of the opalescent Incisal and Translucent powders.

#### Contents P. 3 1. Notes 2. System components P. 3 3. Application P. 12 4. Technical advice for various porcelains 4-1. VINTAGE ZR Margin Porcelain P. 23 4-2, VINTAGE ZR Cervical Trans P. 26 4-3. VINTAGE ZR Whitening Set P. 27 4-4. VINTAGE ZR Correction Porcelain P. 27 5. Specifications 5-1. Firing schedule P. 28 5-2. Physical Properties P. 29 6. Troubleshooting P. 30

#### Notes

#### 1-1 Notes

- (1) Use of eye-protective glasses is recommended for contouring work.
- (2) Use of dust extractor or mask is recommended for contouring work.
- (3) This product must only be used for the intended purpose.
- (4) This product must only be used by dental professionals.

#### 1-2. Important Notes

- (1) If allergic reactions occur such as eruption or skin inflammation while using this product, discontinue use immediately and seek medical advice.
- (2) Avoid contacting soft tissues, skin or eyes. In case of eye contact, rinse immediately with copious amounts of water and seek medical advice.

#### 2 System components

#### 2-1. Reproduction of life-like shades

- (1) Restorations with enhanced esthetics can be fabricated thanks to the wide ranging shade system such as Cervical Trans and/or Opal Porcelain.
- (2) More life-like enamel shades can be reproduced using Opal Porcelain with the simplified 2-layer technique.
- (3) Opaque Liner enables more stable shades to be reproduced, regardless of the die shade.

#### 2-2. Fluorescence resembling that of natural teeth

- (1) Fluorescence resembling that of natural teeth Vintage ZR is uranium-free and especially biocompatible.
- (2) Margin and Cervical Trans porcelains are especially fluorescent for creating restorations with life-like cervical areas.



#### 2-3. System and shades

SYSTEM	SHADES
Opaque Liner (23 shades) 5g	A1O, A2O, A3O, A3.5O, A4O, rootAO, B1O, B2O, B3O, B4O, C1O, C2O, C3O, C4O, D2O, D3O, D4O, W1O, W2O, W3O, OM-Y, OM-LP, OM-DP
Opaque Dentin (9 shades) 15g and 50g	OD-N, OD-A3, OD-rootA, OD-B2, OD-B4, OD-C2, OD-C4, OD-D3, OD-W1
Margin (11 shades)	CLM, NM, A3M, rootAM, B2M, B4M, C2M, C4M, D3M, LPM, W1M
Body (20 shades) 15g and 50g	A1B, A2B, A3B, A3.5B, A4B, rootAB, B1B, B2B, B3B, B4B, C1B, C2B, C3B, C4B, D2B, D3B, D4B, W1B, W2B, W3B,
Opal (5 shades) 15g and 50g	Opal 56, Opal 57, Opal 58, Opal 59, Opal 60
Opal Effect (8 shades) 15g and 50g	Opal T, Opal SL, Opal WE, Opal MI, Opal OC, Opal AM-R, Opal AM-Y, Opal AM-V
Enamel Effect (5 shades) 15g and 50g	BT, OT, PT, GT, T-Glass
Cervical (4 shades) 15g and 50g	AC, BC, CC, DC
Cervical Trans (5 shades) 15g and 50g	CT-CL, CT-W, CT-A, CT-B, CT-R
Color Effect (8 shades)	MP, MY, MIv, RED, Y, O, G, W
Gum (2 shades)	Gum-LP, Gum-DP
Correction (3 shades)	ADD-ON B, ADD-ON T, CPM FINE

#### 2-4. Components

#### ① Opaque Liner (23 shades, 5g each)

#### Opaque Liner is used to create the base shade.

Apply on the zirconia coping to produce a base for each shade. Opaque Liner is a paste which is easily applied in thinner layers. It masks discolored abutment teeth or metal cores and can be applied as a base shade for the Zirconia core frame. 3 modifier shades are available for reproducing a wider range of shades. The layer thickness and viscosity are easily adjusted as this material is supplied in paste form.

· OM-Y : Yellowish shade · OM-LP: Light pinkish shade · OM-DP: Deep pinkish shade

#### Opaque Dentin (9 shades, 15g and 50g each)

This porcelain has the same shade as body porcelain, but is more opacious.

It is used in lingual areas or the gingival aspects of bridge pontics where only limited space is available for the porcelain.

- · OD-N: Diluent color porcelain for mixing with basic Opaque Dentin shades
- · OD-W1: This porcelain is used for Whitening shades.

#### 3 Margin (11 shades, 15g each)

This porcelain has the same shade as body porcelain, but has a higher firing temperature and increased fluorescence.

It is used for optimizing the marginal areas of zirconia copings or building up porcelain margins.

- · CLM: Transparent shade-also for mixing with basic Margin porcelain shades for adjusting the transparency.(Maximum mixing ratio:40%)
- · NM : Diluent color porcelain for mixing with basic Margin porcelain shades.
- · LPM: Light pinkish shade for mixing with basic Margin porcelain shade.
- · W<sub>1</sub>M: This porcelain is used for Whitening shades.

#### 4 Body (20 shades, 15g and 50g each)

This porcelain is used to reproduce dentin shades.

#### 5 Opal (5 shades, 15g and 50g each)

This enamel porcelain transmits light similar to natural enamel (opal effect). Applying it in two layers, together with Body porcelain, enables life-like enamel shades to be reproduced.

System components

Opal Effect (8 shades, 15g and 50g each)

This enamel effect porcelain transmits light similar to natural enamel (opalescence).

· OPAL T (Translucent):

Regular opalescent translucent porcelain.

· OPAL SL (Superlucent):

A slightly bluish porcelain with higher opalescent translucency.

· OPAL WE (White Enamel):

A slightly whitish porcelain for use in marginal or interproximal areas.

· OPAL MI (Milkv):

Milky shade porcelain for use in molar cusps or whitish areas.

· OPAL AM-R (Amber Red):

A slightly reddish amber porcelain for reproducing enamel shades.

· OPAL AM-Y (Amber Yellow):

A slightly vellowish amber porcelain for reproducing enamel shades.

· OPAL AM-V (Amber Violet):

A slightly violet amber porcelain for reproducing enamel shades.

· OPAL OC (Occlusal):

A slightly dull vellowish porcelain for use in the occlusal areas of molars.

#### The state of the s

Translucent enamel effect porcelain without opalescence.

- · BT (Blue Translucent): Bluish translucent porcelain.
- · OT (Orange Translucent): Orangish translucent porcelain.
- · PT (Pink Translucent): Pinkish translucent porcelain.
- · GT (Grey Translucent): Greyish translucent porcelain.
- · T-Glass: Highly translucent (glass-like) porcelain.

#### ® Cervical (4 shades, 15g and 50g each)

Cervical porcelain for reproducing cervical areas. When mixed with Body porcelain, especially dark shades such as A4 or B4 are more effective.

9 Cervical Trans (5 shades, 15g and 50g each)

This translucent cervical porcelain has a slightly lower firing temperature than Body porcelain. It reproduces deeper translucent shades in cervical areas and creates smooth surfaces for tissue compatibility. It is highly fluorescent.

- · CT-CL: Translucent porcelain.
- · CT-W : A slightly translucent porcelain, used for turning cervical areas
- · CT-A : Orangish translucent porcelain for use with A shade groups mixed with CT-CL.
- · CT-B : Yellowish translucent porcelain for use with B shade groups mixed with CT-CL.
- · CT-R : Reddish translucent porcelain for use with R shade groups mixed with CT-CL.

#### 2-4. Components

#### 10 Color Effect (8 shades, 15g each)

This Effect porcelain can be used with or without Body porcelain, as required.

· MP (Mamelon Pink):

Pinkish and intensive porcelains for reproducing mamelons in the incisal areas of younger patients' teeth.

· Mlv (Mamelon Ivorv):

Ivory and intensive porcelains for reproducing mamelons in the incisal areas of middle-aged patients' teeth.

· MY (Mamelon Yellow):

Yellowish and intensive porcelains for reproducing mamelons in the incisal areas of elderly patients' teeth.

- · RED (Red): Pinkish porcelain.
- · Y (Yellow) : Yellowish porcelain.
- · O (Orange): Orangish porcelain.
- · G (Grey) : Greyish porcelain.
- · W (White) : Whitish porcelain.

#### ① Gum (2 shades, 15g each)

This pink shaded porcelain is for reproducing gum shades and is fired at lower temperatures.

Due to the lower firing temperature, it can be used after firing the regular porcelain.

- · Gum-LP (Light pink): Lighter pink shaded porcelain.
- · Gum-DP (Dark pink): Darker pink shaded porcelain.

#### © Correction (3 shades, 15g each)

Can be used in small amounts for correcting after contouring or self-glazing.

- · ADD-ON B: Shade A3B Body correction porcelain.
- · ADD-ON T: Translucent porcelain for correcting enamel areas.
- · CPM Fine: Finer particle porcelain than ADD-ON B. Used for adjusting of marginal fit after glazing.

#### ③ VINTAGE AL/ZR Opaque Liner Liquid (3mL)

Opaque Liner mixing liquid for adjusting the viscosity of the paste.

W VINTAGE Modelling Liquid (50mL, 500mL)

Mixing liquid for the VINTAGE porcelain system (except Opaque Liner). Prevents mixed powder from drying and enhances the handling properties when building up.



#### VINTAGE ZR Margin Porcelain Set

13 shades

Base shades (10 shades / 15g): CLM, NM, A3M, rootAM, B2M, B4M, C2M, C4M,

D<sub>3</sub>M. W<sub>1</sub>M

Effect shades (1 shade / 15g) : LPM

Correction (2 shades / 15g) : ADD-ON B, CPM FINE

VINTAGE CPM Modelling Liquid (1 bottle / 3mL)

VINTAGE Margin Porcelain Isolation Liquid (1bottle / 7mL)



#### VINTAGE ZR Color Effect Set

13 shades

Opaque Liner Effect shades (3 shades / 5g) : OM-Y, OM-LP, OM-DP

Color Effect (8 shades / 15g) : MP, MY, MIv, RED, Y, O, G, W

Gum (2 shades / 15g) : Gum-LP, Gum-DP



#### VINTAGE ZR Intro Set

8 shades

Opaque Liner (2 shades / 5g) : A<sub>2</sub>O, A<sub>3</sub>O

Cervical (1 shade / 15g) : AC

Body (2 shades / 15g) : A<sub>2</sub>B, A<sub>3</sub>B

Opal (2 shades / 15g) : OPAL 58, OPAL 59

Opal Effect (1 shade / 15g) : OPAL T

VINTAGE AL/ZR Opaque Liner Liquid (1 bottle / 3mL)



#### Individual products

Opaque Liner (23 shades / 5g)
Margin (11 shades / 15g)
Opaque Dentin (9 shades / 15g, 50g)

Body (20 shades / 15g, 50g)

Opal (5 shades / 15g, 50g)

Opal Effect (8 shades / 15g, 50g)Enamel Effect (5 shades / 15g, 50g)

Color Effect (8 shades / 15g)

**Cervical** (4 shades / 15g, 50g)

Cervical Trans (5 shades / 15g, 50g)Gum (2 shades / 15g)

Correction (3 shades / 15g)

#### Related products

● VINTAGE AL/ZR OPAQUE LINER LIQUID (3mL)

• VINTAGE MODELLING LIQUID (50mL, 500mL)

● VINTAGE CPM MODELLING LIQUID (3mL)

VINTAGE MARGIN PORCELAIN ISOLATION LIQUID (7mL pen type)

VINTAGE PORCELAIN ISOLATION LIQUID (10mL)

VINTAGE AL/ZR COLOR INDICATOR (7 types)

- Opaque Liner
- Body
- Enamel (Opal, Opal Effect, Enamel Effect)
- Margin (Including CPM FINE)
- Opaque Dentin
- Color Effect (Opaque Liner Effect, Color Effect)
- Cervical, Cervical Trans, Correction

#### VINTAGE Art

- Basic Color Set (17 colors/3g each, VINTAGE Art Stain Liquid / 50mL)
- Effect Color Set (16 colors/3g each, VINTAGE Art Stain Liquid / 50mL)
- VINTAGE Art Refills (32 colors/3g each)
- VINTAGE Art Stain Liquid (50mL)





System components

## 3-1. VINTAGE ZR Shade Charts

Table 1 - Basic Shades

Shade	A1	A2	A3	A3.5	A4	rootA
Opaque Liner	A10	A2O	АзО	A3.5O	A4O	rootAO
Cervical	-	-	A3B : 2 AC : 1	A3.5B : 1 AC : 1		AC
Body	A1B	A2B	АзВ	Аз.5В	A4B	rootAB
Opal	57	58	59	59 : 1 60 : 1	60	60

Shade	B1	B2	B3	B4
Opaque Liner	B10	B <sub>2</sub> O	ВзО	B40
Cervical	ı	ı	B <sub>3</sub> B : 1 BC : 1	ВС
Body	B1B	B <sub>2</sub> B	ВзВ	B4B
Opal	57	58	59	60

Shade	C1	C2	C3	C4	D2	D3	D4
Opaque Liner	C10	C2O	СзО	C4O	D2O	D3O	D4O
Cervical	-	C <sub>2</sub> B : 2 CC : 1	C <sub>3</sub> B : 1 CC : 1	CC	D <sub>2</sub> B : 1 DC : 1	D3B : 1 DC : 1	DC : 2 BC : 1
Body	C1B	C2B	СзВ	C4B	D <sub>2</sub> B	DзB	D4B
Opal	58	58	59	60	58	59	59

Table 2 - Whitening Shades

Shade	W1	W2	W3
Opaque Liner	W1O	W2O	WзO
Cervical	-	-	-
Body	W1B	W2B	WзB
Opal	56	56 : 2 57 : 1	56 : 1 57 : 2

Shade	1	2	3	3.5	4	root
Α	OD-N	OD-N : 1 OD-A <sub>3</sub> : 1	OD-A3	OD-A3 : 2 OD-rootA : 1		OD-rootA
В	OD-N : 1 OD-B <sub>2</sub> : 1	OD-B <sub>2</sub>	OD-B <sub>2</sub> : 1 OD-B <sub>4</sub> : 1	-	OD-B4	-
С	OD-N : 1 OD-C <sub>2</sub> : 1	OD-C2	OD-C <sub>2</sub> : 1 OD-C <sub>4</sub> : 1	-	OD-C4	-
D	-	OD-N : 1 OD-D3 : 1	OD-D3	-	OD-D3 : 1 OD-B4 : 1	-
W	OD-W <sub>1</sub>	OD-W <sub>1</sub> : 2 OD-N : 1	OD-W <sub>1</sub> : 1 OD-N : 2	-	-	-

Table 4 - Margin porcelain

Shade	1	2	3	3.5	4	root
А	NM	NM : 1 АзМ : 1	АзМ	АзМ : 2 rootAM : 1	A3M : 1 rootAM : 2	rootAM
В	NM : 1 B2M : 1	B2M	B <sub>2</sub> M : 1 B <sub>4</sub> M : 1	-	B4M	-
С	NM : 1 C <sub>2</sub> M : 1	C2M	C <sub>2</sub> M : 1 C <sub>4</sub> M : 1	-	C4M	-
D	-	NM : 1 D3M : 1	DзM	-	DзM : 1 В4M : 1	-
W	W1N	W1M : 2 NM : 1	W <sub>1</sub> M : 1 NM : 2	-	1	-

Application

Application



Adjusting with Diamond points.

NOTE: Excess pressure, coarse diamond points, and high speed grinding lead to chipping and cracking.



Shaping and finishing with Shofu Core Master (diamond impregnated polisher).



After heat treatment.

Application



650°C

50~60 °C / min

1000°C Hold 5min.

Preheating zirconia copings

- Hint
- For adjusting coping, use water cooling to avoid over-heating.
  - After adjusting coping, heat treatment is necessary.


Note For other type of metal free coping, such as glass infiltrated system, use of VINTAGE AL is recommended.

#### 3-3. Layering diagram


#### Basic layering 1 (when Opaque Liner is used)

In case of Zirconia coping, materials and production method are different depending on the manufacture, so there are varieties in shade and translucency. Before application, adjustment of shade of the coping is necessary based on the desired shade (foundation work).

#### For anterior teeth

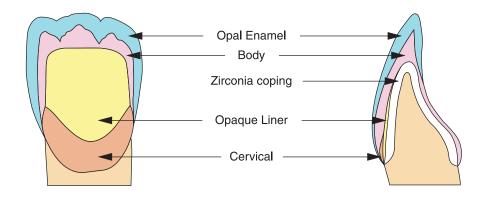

#### For posterior teeth

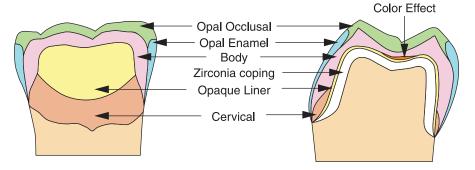

Layering structure using Opaque liner




Application


Application

### Basic layering 2 (when Opaque Liner is not used)

In cases with no discolored teeth, build-up without using Opaque Liner and apply Cervical porcelain from the cervical to incisal areas. For darker shades, apply Stain, fire it to fix in place and create the base shade of the coping before applying Cervical porcelain.

#### For anterior teeth

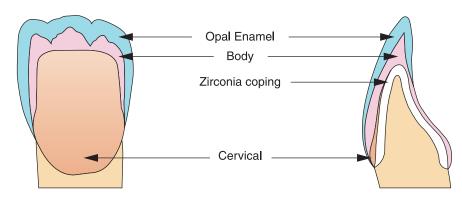

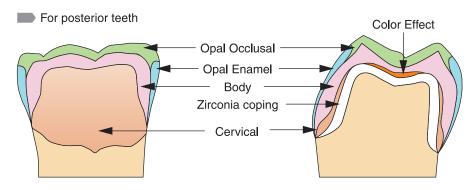

Layering structure without Opaque Liner

#### Hint Foundation work

It is a procedure to adjustment shade of the coping. In this work, Opaque Liner is used for the shade foundation and staining is recommended for the individual adjustment of the shade.

#### 3-4. Basic layering

## Shade Foundation

# When using Opaque Liner (1) First Opaque Liner firing

In case of discolored teeth or where a metal post has been placed, darker areas should be masked with Opaque Liner. Apply Opaque Liner to cover the whole zirconia coping and fire it.

#### (2) Second Opaque Liner firing

After firing the first layer of Opaque Liner, apply a second layer to mask the zirconia coping.

#### Note

- As the Opaque Liner liquid may separate, always mix it before use.
- If bubbles appear in the Opaque Liner, please note the following:
- Please avoid applying Opaque Liner in excessively thick layers.
- Dry thoroughly before firing.
- Avoid placing copings coated with Opaque Liner on a hot firing tray.

#### (3) Firing Cervical porcelain

Apply Cervical porcelain to the cervical area and fire.



Application of Opaque Liner



Firing Opaque Liner



Application of Cervical porcelain



After firing Cervical porcelain

Hint

◆ The basic shade of Opaque Liner can be optimized by using Shofu Porcelain Stain (Shade No. 41-49).



adjacent tooth.

Cervical

(1) Application of Body porcelain

Where no Opaque Liner is used

(1) Firing Cervical porcelain

Cervical porcelain.



Apply Body porcelain and condense it. The shape should match that of the

After firing

Application and firing of Body and Enamel porcelains

Prepared teeth which are not discolored can be restored without using

Opaque Liner. In such cases Cervical porcelain is applied and extended

from the cervical area to the incisal edge. For darker shades, apply Stain,

fire it to fix in place and create the base shade of the coping before firing

After staining

Application of Body porcelain

 Application of Body porcelain We recommend condensing this porcelain more than metal-ceramics. ① Cut back to1/3 point from incisal top.






2 Cut 2/3 point from incisal top.









4 Add mamelon (fingerlike) structure.



**5** The correct Body shape.







Application



Application

Application


- (3) Application of Opal porcelain
- ① Opal porcelain must be overdimensioned to compensate for firing shrinkage.







② Cut back the lingual incisal edge to confirm the shape of the dentin.







③ Build up the reduced lingual incisal edge with Opal porcelain.






Hint 
Outting back the lingual incisal edge
Check that the Body and Enamel porcelains have not blended and
are still layered separately. If the layer is interrupted or the individual
layers blend, the incisal area will not be properly translucent.

#### (4) Building-up the interproximal area

Remove the crown from the model, build-up Opal Porcelain to the interproximal area and condense. Covering the entire surface with opal porcelain creates a natural looking shade. (Wrap around effect)



Build up of interproximal area

Hint

Wrap around effect Coat the labial, lingual incisal, and interproximal surfaces with Opal Porcelain. Coating the entire surface with Opal Porcelain creates depth and translucency of shade.





\*\* The porcelain used in the photo has stronger pigments than the actual porcelain - this enables the positioning of the individual layers to be depicted more clearly.

#### (5) Firing

After building-up fully, adjust the shape and remove the excessive porcelain from the cervical area with a dry brush. Then remove the porcelain from inside the crown and fire.



#### (6) Contouring

After firing, contour the crown with Dura Green Stones and/or CeraMaster, SoftCut polishers and, if necessary, adjust the shade with VINTAGE Stain before glaze firing.









20

# ZR

Application

# (7) Finish Anterior teeth

By direct comparison, the VINTAGE ZR restoration matches perfectly with the Shade Guide.







#### Posterior teeth





Bridgework






### 4 Technical advice for various porcelains

#### 4-1. VINTAGE ZR Margin Porcelain

VINTAGE ZR Margin porcelain is used for adjusting zirconia frames. It eliminates white lines along the margins of zirconia copings and easily reproduces the marginal shade.

#### (1) Adjusting an zirconia coping

The labial margin of a zirconia coping can be adjusted with a diamond point or Shofu Core Master.

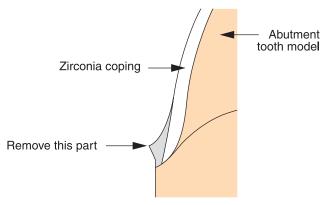

Adjusting a zirconia coping

#### (2) Application of Margin Porcelain Isolation Liquid

Apply one layer of Margin Porcelain Isolation Liquid to the marginal area of the working model and remove excess liquid by air.



Application of Margin Porcelain Isolation Liquid

• If Margin Porcelain Isolation Liquid is applied excessively, inside of the coping might become black after firing process.



#### (3) Application of Margin porcelain

Place the crown on the working model and apply Margin porcelain either mixed with distilled water or CPM Modeling liquid (for small corrections), and condense it.

After contouring, dry it with a hair dryer, remove

the crown from the working model and fire it.











(4) Second build-up and finish of Margin porcelain

After firing, apply additional Margin porcelain where necessary and condense it. Then remove the crown from the working model and fire it. If necessary, please repeat this procedure to fix the margin area.







Finish of Margin porcelain

Margin Layer

The layer of Margin porcelain applied to the margin area should be as thin as possible, which is different to when applying metalceramic Margin porcelain. If the layer is too thick, the full strength of the zirconia coping may not be obtained.







Metal coping



Technical advice for various porcelains

CT-CL: Translucent porcelain.

CT-W: Slightly translucent porcelain for creating

whitish cervical areas.


CT-A: Orange translucent porcelain for creating the

A shade group when mixed with CT-CL.

CT-B: Yellowish translucent porcelain for creating the B shade group when mixed with CT-CL.

CT-R: Reddish translucent porcelain for creating

the R shade group when mixed with CT-CL.



Comparison of fluorescence in cervial area.

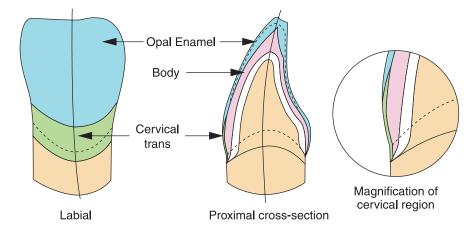


Figure 6 - Cervical trans build-up

Cervical Translucency

In order to enhance the translucency of the cervical area and to increase tissue-compatibility, build-up Cervical Trans in the cervical area and fire with Opal Enamel porcelain. Since the firing temperature is set lower than that of enamel porcelain, smooth surfaces can be obtained.

VINTAGE ZR includes Whitening Porcelain for bleach shades. It reproduces shades which are brighter and lighter than A1, previously impossible with conventional porcelain.



Shade comparison of W1, W2, W3, and A1

#### 4-4. VINTAGE ZR Correction porcelain

VINTAGE ZR Correction porcelain is used for adding material when needed during the biscuit bake, contouring, or glazing.

- If the crown shrinks excessively during the biscuit bake
  - Contour and clean the surface before applying Correction porcelain. Then fire in air to self-glaze.
- If the shrinkage is discovered after self-glazing
  - Biscuit bake (in vacuum) the Correction porcelain before contouring, finishing and polishing with CeraMaster, SoftCut polishers or Dura Polish Dia.

#### Correction

If the crown has shrunk considerably, apply Body or Opal porcelain and proceed with a regular 2nd firing.



Technical advice for various porcelains

Technical advice for various porcelains

#### 5-1. Firing schedule

#### Table 6 - Firing schedule table

Type of porcelain	Drying time (min.)	Temperature raising speed (°C /min.)	
1st Opaque Liner	7~8	45	500°C 920~940°C 1min.
2 <sup>nd</sup> Opaque Liner	7~8	45	500°C 920~940°C 1min.
Cervical	5~6	45	650°C 900~920°C 1min.
1 <sup>st</sup> Body, Enamel	5~6	45	650°C 900~920°C 1min.
2 <sup>nd</sup> Body, Enamel	5~6	45	650°C 900~920°C 1min.
1 <sup>st</sup> Margin	5~6	45	650°C 1030~1050°C 1min.
2 <sup>nd</sup> Margin	5~6	45	650°C 1030~1050°C 1min.
Self Glaze	5~6	45	650°C 900~920°C 0-0.5min.
1 <sup>st</sup> Gum	5~6	45	650°C 860~880°C 1min.
Gum glaze	5~6	45	650°C 860~880°C 1min.
1st Correction	5~6	45	650°C 860~880°C 1min.
Correction Glaze	5~6	45	650°C 860~880°C 1min.
			Vacuum firing

#### PLEASE NOTE:

Firing conditions vary due to the different designs and operating voltages of porcelain furnaces. It is essential to carry out test firings before using the porcelain for actual restorations.

Heat rate

As the heat conductivity of a zirconia coping is low compared with that of a metal coping, it is advisable to set the furnace to a low heat rate.

Firing in the air

#### 5-2. Physical Properties

(1) Coefficient of thermal expansion and Glass transition point

		Coefficient of Thermal Expansion (25~500°C)	Glass Transition Point	
Opaque Liner	2.Firing	9,3 x 10 <sup>-6</sup> K <sup>-1</sup>	620°C	
Opaque Linei	4.Firing	9.5 X 10 °K	0200	
Margin	2.Firing	9.3 x 10 <sup>-6</sup> K <sup>-1</sup>	635℃	
Margin	4.Firing	9.3 X 10 - N	0000	
Pody	2.Firing	9.4 x 10 <sup>-6</sup> K <sup>-1</sup>	605℃	
Body	4.Firing	9.4 X 10 - N	0050	
Cervical Trans		9.4 x 10 <sup>-6</sup> K <sup>-1</sup>	595℃	
Cervical Italis	4.Firing	9.4 x 10 °K	595 C	
Correction	2.Firing	9,4 x 10 <sup>-6</sup> K <sup>-1</sup>	585℃	
Correction	4.Firing	9.4 X 10 °K	363 C	

#### PLEASE NOTE:

- As VINTAGE ZR has a different coefficient of thermal expansion to those of VINTAGE, VINTAGE HALO or VINTAGE AL never mix or combine them.
- For other type of metal free coping, such as glass infiltrated system, use of VINTAGE AL is recommended.

(2) Solubility Test (ISO Specification: Under 100 µg / cm²)

	Solubility amount (µg / cm²)
Body, Enamel	14.8



